



Photocatalytic Degradation of 4-Chlorophenol by Titanium Dioxide: Role of Annealing Temperature and Morphology

*TUM, PK; KARIUKI, DK

School of Physical Sciences, Department of Chemistry, University of Nairobi, P.O Box 30197-00100, Nairobi, Kenya

**Corresponding Author Email: patricktum@uonbi.ac.ke*

ABSTRACT: This work investigates the degradation rate of 4-chlorophenol using Titanium dioxide photocatalysts. Chlorophenols and their compounds are a nuisance as they are recalcitrant to degradation in the environment. Three morphologically different Titanium dioxide catalysts, A, B and C, were immobilized on microscopic glass at a layer of 0.5 mg/cm² and annealed between 500-700°C. The three different TiO₂ powders were characterized using Scanning Electron Microscopy, X-Ray Diffraction and Brunauer Emmett Teller to determine their specific surface area, crystalline and particle sizes. A four-position photocatalytic reactor illuminated by two Ultra violet lamps of wavelength range 320-400 nm and intensity I = 27.87 mW/m² was used to degrade the 4-Chlorophenol in 2 hrs. Aliquots of the degraded 4-chlorophenol were drawn every 30 minutes and analyzed using UV-Vis spectroscopy at λ=226 nm. The optimum annealing temperature of all TiO₂ was found to be 650°C, with type B of hexagonal morphological structure and particle size of 28±2nm having the highest 4-chlorophenol degradation rate, of 71.21%.

DOI: <https://dx.doi.org/10.4314/jasem.v24i1.1>

Copyright: Copyright © 2020 Tum and Kariuki. This is an open access article distributed under the Creative Commons Attribution License (CCL), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Dates: Received: 30 November 2019; Revised: 20 December 2019; Accepted: 23 December 2019


Keywords: Photocatalytic, 4-chlorophenol, annealing, morphology

Chlorinated phenols are categorized as first degree pollutants due to their persistent toxicity, suspected carcinogenicity and mutagenicity. Chlorophenols (CPs) in general, when released into the environment poses serious ecological problems to all living organisms (Movahedian *et al.*, 2008). Among the chlorophenols, 4-chlorophenol has attracted a lot of interest owing to its direct relevance to the environment and its unique photochemical characteristic (Krysa *et al.*, 2006). Chlorophenols find their way into water systems as a result of discharge from chemical industries, have proved resistant to conventional chemical and biological treatments. Some of the industries from which large volumes of chlorophenols are discharged include; petroleum refining, production of pesticides, paint, plastic, resins, textiles, iron-ore processing, solvent synthesis and pharmaceutical productions (Gomez *et al.*, 2009; Movahedian *et al.*, 2009; Olaniran and Igbinsosa, 2011; Pera-Titus *et al.*, 2004; Pi *et al.*, 2007). As a result of water pollution, the sustainable approach to water sources management should therefore include treatment technologies that reduce the negative effects and promote sustainable use of water resources by facilitating recycling and reusing of wastewater (Catrinescu *et al.*, 2011). Advanced Oxidation Processes (AOPs) is one such process that constitute a collection of established treatment technologies which depend on the formation of hydroxyl radicals ($\cdot\text{OH}$) that mineralize non-selectively all contaminants into carbon dioxide and water (Assadi and Eslami, 2010; Gaya *et al.*, 2009; Dan *et al.*, 2004). Researchers have investigated on the removal phenolic compounds using several techniques that include; Ultra-violet/H₂O₂, Ultra-violet/catalyst,

photo-Fenton process, MW/NiO, Ultra-violet/H₂O₂/TiO₂, O₃/ZnO, Graphite and graphene oxides, Microwave/Ultra-violet and UV/O₃/TiO₂ (Marianna, 2006; Lin *et al.*, 2008; Ghaly *et al.*, 2001; Kuo and Lin, 2009; Lai *et al.*, 2007; Chiou *et al.*, 2007; Dixit *et al.*, 2010; Tabatabaei *et al.*, 2011; Bustos-Ramirez *et al.*, 2015; Seo *et al.*, 2017; Gimeno *et al.*, 2005). In addition, the use of microbial cultures *Alcaligenes* in a fermenter has been reported by (Westmeier and Rehm, 1987) to remove 4-Chlorophenol in wastewater. These methods have largely not been very effective and there is need for further research for the effective and economical removal of 4-Chlorophenol from wastewater. This work investigates the role of annealing temperature in the UV/TiO₂ treatment system to degrade 4-Chlorophenol in wastewater. This work anticipates that the optimization of Titanium dioxide's mechanical and chemical properties as well as illumination with ultraviolet light improves the catalytic activity, hence the degradation rate of 4-Chlorophenol. At annealing temperatures of 500-700°C, TiO₂ morphology transforms from anatase to rutile phase, thereby improving its photocatalytic activity. Anatase TiO₂ is mostly used for environmental management, such as water purification, wastewater treatment and water disinfections (Carp *et al.*, 2004; Eslami *et al.*, 2007). It is biologically and chemically inert, stable with respect to photo and chemical corrosion, low cost, active over a wide range of pH, high refractive index, efficient and long-term stability (Ghosh *et al.*, 2009). A draw-back in the application of TiO₂ is its high band gap energy of 3.2 e.V, that allows titanium dioxide to absorb only UV light of wavelength lower than 388

**Corresponding Author Email: patricktum@uonbi.ac.ke*

nm thereby reducing solar light harvesting efficiency down to 5% (Ajmal *et al.*, 2014; Gaya *et al.*, 2009; Barnes *et al.*, 2010). Anatase also has a low mineralization level that is acquired when on large-scale applications and therefore requires a final polishing stage (Gimeno *et al.*, 2004). These shortcomings have renewed efforts to research on reliable and more effective catalysts (Catrinescu *et al.*, 2011; Li *et al.*, 2009). Photocatalytic oxidation processes are related to catalytically active metal oxides such as ZnO, TiO₂, and ZrO₂ which are semiconductors and remove contaminants in wastewater (Lo *et al.*, 2004). They are mainly the oxides of transition metals (Lai *et al.*, 2008; Stoyanova and Christoskova, 2011; Stoyanova *et al.*, 2003). The equations below indicate the reactions that take place when TiO₂ reacts as a semi-conductor.



The contaminant in this study, 4-Chlorophenol contains pesticide properties. It is a characteristic faint yellow liquid with an unpleasant, penetrating odour, molecular mass $M_r = 128.56 \text{ g.mol}^{-1}$ with a chemical formula C₆H₅OCl. The structural formula of 4-Chlorophenol is shown in figure 1 below.




Fig 1: 4-Chlorophenol

MATERIALS AND METHODS

Chemicals: Three different types of Titanium dioxide powder were sourced from Sigma-Aldrich and identified as A, B & C. Lanthanum hexaboride and 4-Chlorophenol of purity 99% was also obtained from Sigma - Aldrich.

Equipment: UV/Vis spectrophotometer model 4000 from Shimadzu Ltd, UV light intensity meter, X-ray diffractometer and Scanning Electron Microscope model Tescan VEGA3 equipment were used

Methods: Morphological Characterization of TiO₂ powder catalysts using Scanning Electron Microscopy, X-Ray diffraction and Brunauer Emmett-Teller procedures are explained here below.

Scanning Electron Microscopy (SEM) – Crystal size: A Tescan VEGA3 Scanning Electron Microscope equipped with a field emission source was preferred over regular SEM with Lanthanum hexaboride filament as a high voltage source for morphological characterization. This is because of its high resolution and brightness at low accelerating voltages that allows

for clearer images. Prior to SEM, the samples were first mounted on an aluminum stub using a double sided carbon tape, and then coated with a thin layer of 10-30 nm composed of 60:40 gold-palladium alloy by means of vacuum sputtering coating using a Denton Desk 1 Sputter-Coater under a 70 mtorr vacuum. Other conditions included: (SEM HV-20.0 kV, view field-6.36 μm and SEM mag 30.0 kx).

Two sample of each TiO₂ powder were inscribed for identification. The samples were dried at an oven 60°C for 3 hours. The samples were loaded into the SEM and blown with inert nitrogen gas to protect any further oxidation reactions. The acceleration voltage was set at 20 KV, lowest magnification (30X) and TV mode. The coarse focus was switched on and the focus knob adjusted to a safe working distance of 14 mm. The focus was switched to slow scan mode and magnification increased. The samples stage was brought up slowly by pressing z-axis UP key. The variable button was opened up to open a small variable window on the screen. The image was focused within the small screen using outer focus ring and inner focus ring until indicator light reaches the middle. The image was previewed and adjusted to contrast and the image set-up window closed. The image acquire icon was clicked to record the image formed and the image saved.

X-Ray Diffractometer (XRD): Crystallite size: Particle sizes are calculated by XRD using the Scherer's equation:

$$l = k\lambda / \beta \cos \theta.$$

Where l is the wavelength of rays, k is a constant taken to be 0, 9 (assuming no crystal distortions in the lattice), β is the width at half maximum of the radians corrected for the instrumental broadening and θ is the diffraction angle in degrees.

Scan parameters: start and end 2q limits 0 -130 - 2q
Step size 0.5 -0.1 - 2q
Step time (1 sec)
Start scan
When scan was completed the file was saved

Brunauer Emmett Teller (BET) – surface area analysis: The BET surface area was measured through a multipoint method utilizing adsorption data in the relative pressure (P/P₀) in the range 0.005-0.3 using nitrogen (99.99%) physico-sorption at 200°C. The system used liquid nitrogen in a 500 ml Dewar flask placed on the stage of the instrument.

ZnO and TiO₂ were heated at 150°C for 2 hours to remove adsorbed water. The resolution of the images formed were set at 80 seconds

Measurement of Irradiation Intensity: The irradiation intensity emitted by UV lamps in the four-hole photoreactor was measured using a light intensity meter positioned at a distance of 0 cm next to the metallic openings from which UV light was irradiated.

The light intensity values were measured at the start and end of each experiment and included in the final value of the rate of photocatalytic degradation. The UV light intensity was measured at $I=27.87 \text{ mW/m}^2$.

UV-Vis spectrophotometric measurements of 4-chlorophenol A stock solution of $0.0001 \text{ mol.L}^{-1}$ in a 500 ml round bottomed flask was made and its absorbance measured using a UV-Vis spectrophotometer. An aliquot of 5 ml 4-Chlorophenol was put into the cuvette and placed in the spectrophotometer. A full UV-Vis scan of 4-Chlorophenol sample was carried out at wavelengths between 200- 600 nm and the spectrum recorded as shown in figure 6.

Calibration curve – 4-chlorophenol Spectral Analysis Molar Extinction Coefficient (ϵ): The coefficient (ϵ) is calculated from the Beer Lamberts law shown in (4) below;

$$A = \epsilon Lc \quad (4)$$

Where: A = is the amount of light absorbed by samples at specific wavelengths (λ); E = is the molar extinction coefficient; L = is the length of cuvette used to measure absorbance; C = is the concentration of the absorbing sample

To determine the extinction coefficient of 4-chlorophenol (ϵ), at 226 nm concentrations of solutions were prepared; $1 \times 10^{-5} \text{ mol.L}^{-1}$, $2.5 \times 10^{-5} \text{ mol.L}^{-1}$, $5 \times 10^{-5} \text{ mol.L}^{-1}$ and $1 \times 10^{-4} \text{ mol.L}^{-1}$. A calibration curve for 4-Chlorophenol using different solution concentrations was obtained and is shown in figure 7 and its molar extinction coefficient calculated.

Photocatalytic degradation of 4-Chlorophenol: The experimental temperature was set at 23°C . The four cuvettes were filled with 25 ml of $1 \times 10^{-4} \text{ mol.L}^{-1}$ of 4-chlorophenol and placed against each of the four holes in the photocatalytic reactor before the UV lamps and the magnetic stirrer were switched on. At the start of the experiment, absorbance was measured and the value recorded for each of the TiO_2 catalyst layers. The fourth cuvette was the experimental control. The absorbance of the solutions was determined at $\lambda=226 \text{ nm}$ and after every 30 minutes of photocatalytic treatment, 5 ml of the 4-Chlorophenol solution was withdrawn from each cuvette, its absorbance recorded till the 120th minute. The rate of 4-Chlorophenol degradation was considered to cover a geometrical area 0.000875 m^2 covered by TiO_2 catalyst immobilized on microscopic glass. The rate was calculated as shown by formula (5) and (6) below and expressed as ($\text{mol.m}^{-2}.\text{W}^{-1}$).

$$r_A = \frac{(c_0 - c_{60})V}{t_{60} - t_0} \cdot \frac{1}{A} \quad (5)$$

Where: r_A = rate of 4-Chlorophenol in degradation ($\text{mol.m}^{-2}.\text{h}^{-1}$); c_o = initial 4-Chlorophenol in concentration (mol.L^{-1}); c_{60} = 4-Chlorophenol concentration after 1 hour (mol.L^{-1}); t = time at which irradiation started (0 hours.); t_{60} = time of irradiation

(1 hour); V = volume of 4-Chlorophenol irradiated in cuvette (0.025 ml); A = irradiated geometric surface area of particulate film (0.000875 m^2); The rate of photodegradation relative to incident UV light intensity is then calculated according to equation 6 below.

$$r_l = \frac{r_A}{I} \quad (6)$$

Where r_l the rate of 4-Chlorophenol photocatalytic degradation ($\text{mol.h}^{-1}.\text{W}^{-1}$) and I is UV light intensity (mW/m^2).

Preparation of TiO_2 coated layers immobilized on microscopic glass: Catalyst suspensions of concentration 10 g.L^{-1} were prepared from the 3 samples; A, B and C in 100 ml volumetric flasks. The suspensions were further homogenized in an ultrasonic bath for 30 seconds to break-up any agglomerates present. A volume of 3.75 ml of the TiO_2 suspensions were taken using a 5 ml syringe and immobilized onto a clean, dry and degreased microscopic glass slides of dimensions $75 \text{ mm} \times 25 \text{ mm}$ and placed on ceramic tile and allowed to dry at room temperature for 1 hour. The coated layers were then dried at 50°C in an oven for 30 minutes to further fixate the catalyst particles onto the glass. The final procedure involved the annealition of the layers attached onto porcelain crucibles in a furnace at $500, 550, 600, 650 \text{ \& } 650^\circ\text{C}$ for a duration of 2 hours. The annealed layers were trimmed to reduce the geometric area covered by the catalyst to 0.000875 m^2 and loading of 0.5 mg/cm^2 . The procedure described above was used to prepare particulate layers for all the three catalysts.

Photocatalytic degradation reactor: The photocatalytic reactor was operated in batch mode and consisted of a magnetic stirrer. Three cuvettes of 30 ml were placed onto the holes illuminating UV light. The stirring rate was set at 900 rotations/min. Each of the cuvettes was filled with 25 ml of 4-Chlorophenol c $1 \times 10^{-4} \text{ mol.L}^{-1}$. The photoreactor was attached to a thermostat to regulate its temperature as shown in figure 2 below. The TiO_2 coated layers prepared from the procedure described in section (2.4.1) were suspended using metallic clips and dipped into cuvettes containing 4-Chlorophenol solutions. The cuvettes consisting of 4-Chlorophenol solutions and TiO_2 coated layers were illuminated with UV light from 2 lamps. The intensity of the UV light was measured by a light intensity meter.

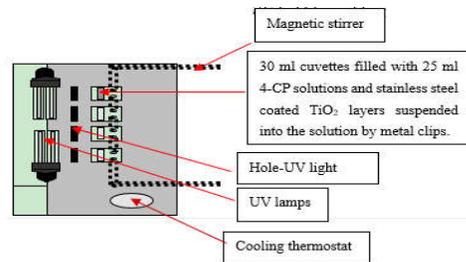


Fig 2: Four-hole Photocatalytic Reactor

RESULTS AND DISCUSSION

Characterization of TiO₂ powder catalysts: The crystalline sizes obtained from XRD measurements and SEM estimations, show that from figure 3, 4 and 5, we observe catalyst individual crystals and agglomerates. The particle sizes of catalyst B (169 nm) were bigger compared to the other catalysts, but had the smallest specific surface area (10 m²/g). Smaller particle sizes were observed in catalyst C (9 nm) and the largest specific surface area (250 m²/g). Catalyst A had particles size of (28 nm) and specific surface area (50 m²/g). The morphological characterization indicates distinct properties between the three powder catalysts.

Table 1: Morphological characterization - (XRD, SEM & BET)

Sample	Agglomerate size (nm) SEM	Crystal size (nm) (XRD)	Specific surface area (m ² /g) (BET)
A	200-300	28	50
B	300	169	10
C	100-300	9	250

Table 1 and figure 3, 4 and 5 presents the results from the morphological characterization of the catalysts used in this study.

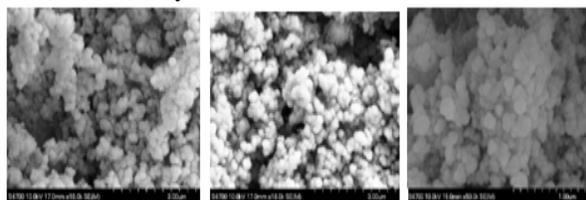


Fig 3: SEM(A)

Fig 4: SEM(B)

Fig 5: SEM(C)

UV-Vis spectra of 4-chlorophenol: Figure 6 below shows a UV-Vis spectrum for 4-Chlorophenol of concentration 1×10⁻⁴ mol.L⁻¹ used to determine λ_(max).

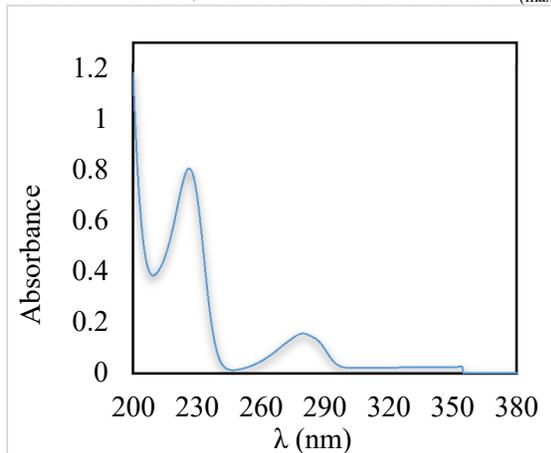


Fig 6: UV-Vis spectrum of 4-Chlorophenol

The scan showed a maximum absorption wavelength peaks at λ= (226 nm and 282 nm) which means 4-Chlorophenol absorbs light in the UV region. The

photocatalytic degradation experiments in this work was determined at λ=226 nm, which was more pronounced compared to λ=282.5 nm. It implies that 4-Chlorophenol has peak absorbance at 226 and 282 nm. This figure is quite close to λ=227 nm and 280 nm reported in literature by (Bustos-Ramírez et al., 2015). Between λ= (300-600 nm). The contaminant in the study 4-Chlorophenol, was noted not to absorb any visible light (λ=390-790 nm) as observed in figure 6. Calibration curve 4-Chlorophenol (Molar Extinction Coefficient (ε))

The Molar Extinction Coefficient was determined through a standard calibration curve plotted in Figure 7 below.

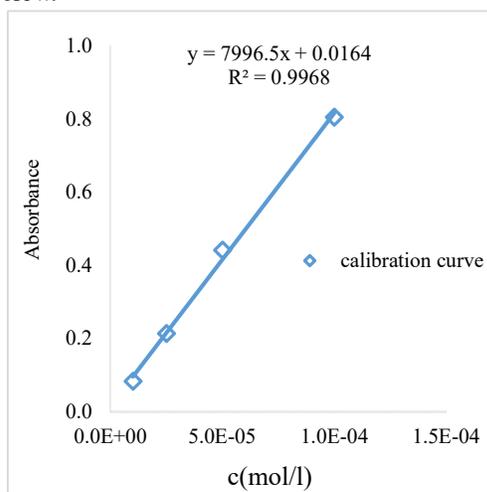


Fig 7: Calibration curve 4-chlorophenol

To determine the extinction coefficient (ε) of 4-Chlorophenol, the following concentrations 4 solutions of various concentrations were prepared from a stock solution of 1×10⁻⁴ mol. L⁻¹. These were, (1×10⁻⁵ mol.L⁻¹, 2.5×10⁻⁵ mol.L⁻¹, 5×10⁻⁵ mol.L⁻¹ and 1×10⁻⁴ mol.L⁻¹). A cuvette of 1 cm unit length and a UV-Vis spectrophotometer, absorbance for these solutions was measured at λ_{max} = 226 nm. Plotting absorbance against concentration, generated a calibration curve with a molar extinction coefficient (ε) of 7996.5 mol⁻¹dm³cm⁻¹.

Photocatalytic degradation of 4 –Chlorophenol: The removal of 4-Chlorophenol was measured by its rate of its photocatalytic degradation. This work studied the effect of catalyst annealing temperature, morphology and its subsequent effect on the rate of degradation. The rates of 4-Chlorophenol was studied using catalysts annealed at temperatures between 500-700°C and recorded in figure 8, 9, 10, 11 & 12. The influence of TiO₂ annealing temperatures on the rates of 4-Chlorophenol degradation are discussed in figure 13 and 14.

Degradation of 4-Chlorophenol using selected TiO₂ catalysts annealed at 500°C: The different types of TiO₂ A, B and C tested for degradation of various

concentrations of 4-Chlorophenol at 500°C are shown in Figure 8.

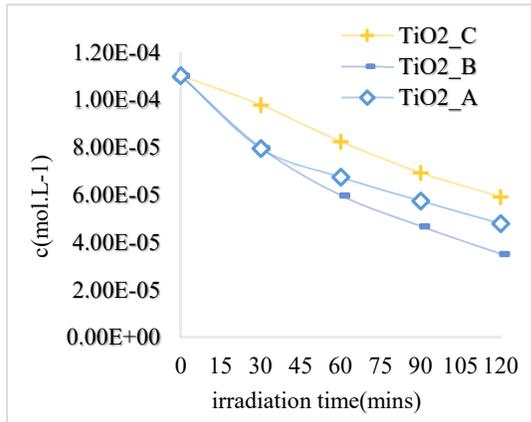


Fig 8: Degradation of 4-Chlorophenol using selected TiO₂ catalysts annealed at 500°C

The results above indicated that at 500°C, optimum rates of 4-Chlorophenol degradation rates was achieved. The B catalyst was the most photocatalytically active and C the least. At this. After 2 hours of UV-TiO₂ photocatalytic degradation system, the removal of 4-Chlorophenol was measured; B-68.02%, C-46.25% and A-56.46%. This result was influenced by the irregular shape of TiO₂ particles at low temperatures causing low kinetic energy that is not sufficient to induce coalescence of the individual TiO₂ grains.

Degradation of 4-Chlorophenol using selected TiO₂ catalysts annealed at 550°C : The degradation experiments were also repeated at 550°C and shown in Figure 9.

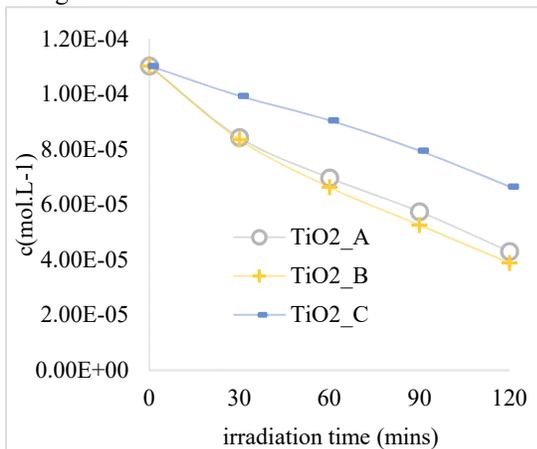


Fig 9: Degradation of 4-Chlorophenol using selected TiO₂ catalysts calcined at 550°C

Figure 9 shows that photocatalyst B of decreasing 4-Chlorophenol was the fastest while C was the slowest. The changes in 4-Chlorophenol concentration after 2

hours were then used to calculate degradation rates as follows; B-64.85%, C-39.68% and A-61.11%. Compared to 500°C, the degradation rates were observed to decrease by an average of 5.08%. This may be affected by the loss of active TiO₂ particle sites on the deposited layers. This implies that photodegradation may also take place at the suspended TiO₂ particles .

Degradation of 4-Chlorophenol using selected TiO₂ catalysts annealed at 600°C: The results of the degradation of 4-Chlorophenol using annealed TiO₂ at 600°C is shown here below.

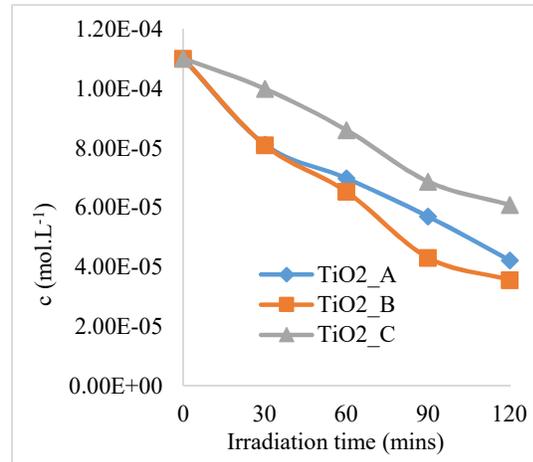


Fig 10: Degradation of 4-Chlorophenol using selected TiO₂ catalysts calcined at 600°C

Figure 10 shows that B catalysts degraded 4-Chlorophenol more rapidly compared to A and C. After 2 hours of UV/TiO₂ photocatalytic treatment, the removal of 4-Chlorophenol was determined to be; B-67.64%, C-44.78% and A-61.68%. Compared to immobilized layers annealed at 550°C, the rate of 4-Chlorophenol degradation increased slightly at 600°C. A possible explanation could be the modification in catalyst morphology as a result of annealing.

Degradation of 4-Chlorophenol using selected TiO₂ catalysts annealed at 650°C: The degradation experiments were also repeated at 550°C and shown in Figure 11. Figure 11 indicate the optimum annealing temperature for the degradation of 4-Chlorophenol was determined to be 650°C. At this calcination temperature, the rates of degradation for 4-Chlorophenol was optimized. Compared to the results shown in figure 8, 9 and 10, B catalyst was most photocatalytically active and C the least. After 2 hours of photocatalytic degradation, the removal of 4-Chlorophenol was measured to be; (B-71.21%, C-43.80% and A-63.61%). At this annealing temperature the TiO₂ crystallite structure is suggested to be modified by annealing temperature and subsequently the rate of 4-Chlorophenol removal.

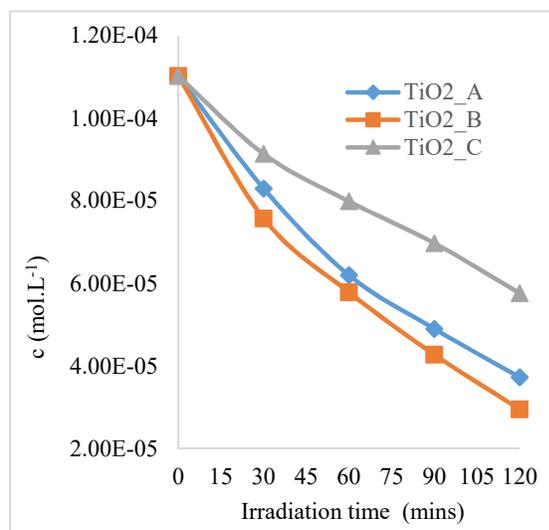


Fig 11: Degradation of 4-Chlorophenol using selected TiO₂ catalysts annealed at 650°C.

Degradation of 4-Chlorophenol using selected TiO₂ catalysts annealed at 700°C: From figure 12 as observed from the other annealing temperatures, B catalyst was the most photocatalytically active and C the least. After 2 hours of photocatalytic degradation, the removal of 4-Chlorophenol was measured at; (B-67.19%, C-35.36% and A-61.36%). At 700°C most likely the crystal grains in the immobilized films would get larger as a result of densification. The rates of 4-Chlorophenol removal declined by 12.98% at temperature interval 650-700°C. This means that annealing temperatures above 650°C have a negative effect on rate of 4-Chlorophenol degradation due to the morphological TiO₂ transformation from anatase to rutile. The rutile phase is less crystalline compared to anatase phase leading to decreased rates of 4-Chlorophenol.

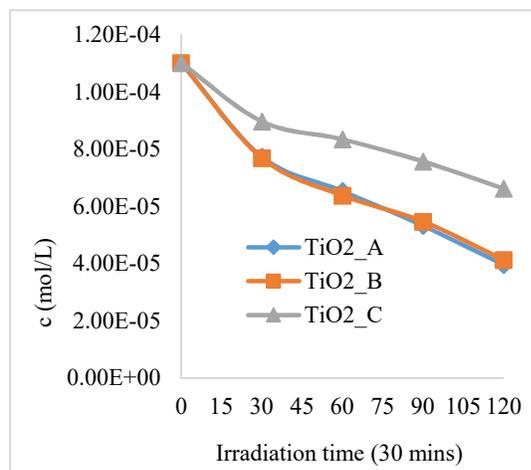


Fig 12: Degradation of 4-Chlorophenol by TiO₂ catalysts annealed at 700°C

Photocatalytic degradation of 4-Chlorophenol $c \times 10^{-4}$ M using TiO₂ catalysts annealed at temperatures between 500-700°C. Figure 13 below analyses the correlation between the rates of 4-Chlorophenol degradation, the type of TiO₂ catalyst and annealing temperatures 500-700°C.

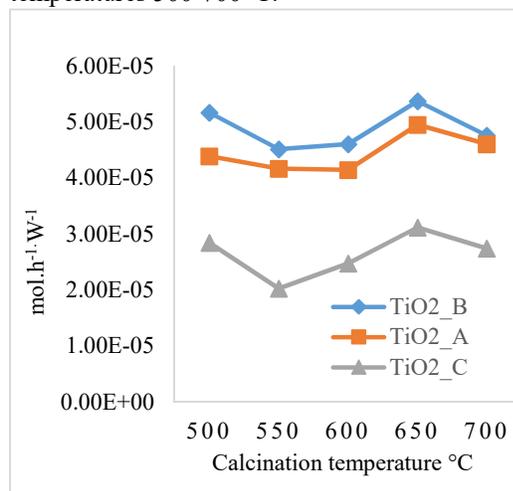


Fig 13: Effect of TiO₂ catalyst calcination temperature on the rate of 4-Chlorophenol removal after 1 hour of photocatalytic treatment.

An increase in calcination temperatures in the range 500-550°C had an average negative effect. 5.08% on the degradation rate of 4-Chlorophenol which can be explained by sintering of catalyst particles that causes it to bind and fuse together causing the particles to grow and form agglomerates. A significant increase 12.98% in 4-Chlorophenol degradation was observed at calcination temperatures between 550-650°C. Between 650-700°C the degradation rates of 4-Chlorophenol decreased by 14.71% due to morphological Phase transformation from anatase to rutile phase at 700°C annealing temperature. The results show that 650°C is optimum calcination temperature to achieve effective degradation of 4-Chlorophenol, the findings show that the following levels of efficiency in removing 4-Chlorophenol was achieved at 650°C; (A-63.61%, C-43.80% and B-71.21%). The findings in figure 13, corroborate the results obtained in figure 8, 9, 10, 11 & 12 that indicate similar trends. The shifting rates of 4-Chlorophenol removal with increased annealing temperatures can be explained as follows; the most influential parameter would be the decrease in the density of structural defects, whereas the decrease in surface area would have a lesser influence in the removal of 4-Chlorophenol. This is caused by the poor adsorption properties of 4-Chlorophenol and density of defects with regards to catalyst surface area for most aromatic contaminants such as 4-Chlorophenol. This means photocatalytic reactions react in the vicinity of TiO₂ and not on its surface. The higher specific surface area of C does not positively affect the rates of 4-Chlorophenol degradation because it does not presumably react principally at the surface.

Effect of TiO₂ calcination temperature on the

concentration of 4-Chlorophenol: Figure 14 shows change in 4-Chlorophenol concentration with increasing calcination temperature between 500-700°C.

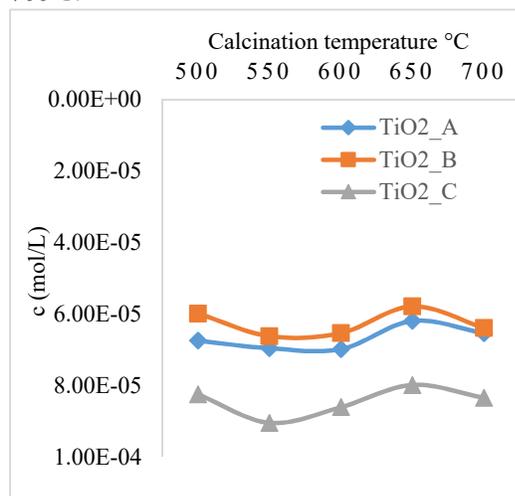


Fig 14: Changes in 4-chlorophenol concentration with selected TiO₂ catalyst after 1 hr. of photocatalytic degradation

The results in figure 14 are similar to the findings obtained in figure 13. Figure 14 shows the correlation between fluctuations in 4-Chlorophenol $c(\text{mol.L}^{-1})$, TiO₂ catalyst and annealing temperature. Furthermore the findings corroborate the results shown in figure 8, 9,10,11,12 & 13. Annealing of TiO₂ catalysts remove defects on the crystalline planes, thereby reducing TiO₂ internal stresses and improving ductility of metallic alloys as observed between annealing temperatures 550-650°C. The reduction in the rates of 4-Chlorophenol above 650°C was caused by morphological transformations from anatase to rutile phase, thus decreasing TiO₂ crystallinity and photocatalytic activity.

Conclusions: Annealing temperature of TiO₂ has a significant influence on the resultant photocatalytic degradation rates of 4-Chlorophenol by the produced immobilized layers. The optimum annealing temperature of TiO₂ was found to be 650°C, with type B of hexagonal morphological structure and particle size of 28±2nm having the highest 4-chlorophenol degradation rate, of 71.21%. The increase of TiO₂ crystal size favours high rates of 4-Chlorophenol degradation, while surface area variation of their layers has little effect on 4-Chlorophenol degradation. The surface morphology of TiO₂ immobilized layers was influenced by its annealing temperature.

Acknowledgements: The authors thank the Department of Inorganic technology, University of Chemistry and Chemical Technology, Prague – Czech Republic for use of Laboratory space and analytical facilities.

REFERENCES

Ajmal, A; Majeed, I; Malik, R N; Idriss, H; Nadeem, M A (2014). Principles and mechanisms of photocatalytic dye degradation on TiO₂ based

photocatalysts: A comparative overview. *Rsc Advances*, 4, (70), 37003-37026.

Assadi, A; Eslami, A; (2010). Comparison of phenol photodegradation by UV/H₂O₂ and photo-Fenton processe. *Environ Eng Manag J.*, 9: 807-812

Barnes, RJ; Riba O; Gardner, MN; Scott, TB; Jackman, SA; Thompson, IP (2010). Optimization of nano-scale nickel/iron particles for the reduction of high concentration chlorinated aliphatic hydrocarbon solutions. *Chemosphere*, 79, 448-454

Bustos-Ramírez, K; Barrera-Díaz, C E; De Icaza-Herrera, M; Martínez-Hernández, AL; Navidad-Rangel, R; Velasco-Santos, C (2015). 4-chlorophenol removal from water using graphite and graphene oxides as photocatalysts. *J. Environ. Health Sci. Engineer.* 13 (33)

Carp, O; Huisman, C L; Reller, A (2004). Photoinduced reactivity of titanium dioxide. *Progress in solid state chemistry*, 32(1), 33-177

Catrinescu, C; Arsene, D; Teodosiu, C (2011). Catalytic wet hydrogen peroxide oxidation of para-chlorophenol over Al/Fe pillared clays (AlFePILCs) prepared from different host clays. *Appl Catal Environ.*, 101, 451-460.

Chiou, C-H; Wu, C-Y; Juang, R-S (2008). Influence of operating parameters on photocatalytic degradation of phenol in UV/TiO₂ process. *Chem Eng J.*, 139, 322-329.

Dixit, A; Mungray, AK; Chakraborty, M (2010). Photochemical Oxidation of Phenol and Chlorophenol by UV/H₂O₂/TiO₂ Process: A Kinetic Study. *Int J Chem Eng Appl.*, 1. 247-250.

Eslami, A; Nasser, S; Yadollahi, B; Mesdaghinia, A; Vaezi, F; Nabizadeh, R (2007). Application of photocatalytic process for removal of methyl tert-butyl ether from highly contaminated water. *Iran J Environ Health Sci Eng.*, 4,215-222.

Gaya, UI; Abdullah, AH; Zainal, Z; Hussein, MZ; (2009). Photocatalytic treatment of 4-chlorophenol in aqueous ZnO suspensions: Intermediates, influence of dosage and inorganic anions. *J Hazard Mater.* 168: 57-63.

Ghaly, MY; Härtel, G; Mayer, R; Haseneder, R (2001). Photochemical oxidation of p-chlorophenol by UV/H₂O₂ and photo-Fenton process. A comparative study. *Waste Manag.* 21, 41-47.

Ghosh, JP; Sui, R; Langford, CH; Achari, G; Berlinguette, CP (2009). A comparison of several nanoscale photocatalysts in the degradation of a common pollutant using LEDs and conventional UV light. *Water Res.*, 43, 4499-4506.

- Gimeno, O; Carbajo, M; Beltrán, FJ; Rivas, FJ (2004). Phenol and substituted phenols AOPs remediation. *J Hazard Mater.* 119, 99-108.
- Gimeno, O; Carbajo, M; Beltrán, FJ; Rivas, FJ (2005). Phenol and substituted phenols AOPs remediation. *J Hazard Mater.* 119, 99-108.
- Gomez, M.; Matafonova, G; Gomez, JL; Batoev, V; Christofi, N (2009). Comparison of alternative treatments for 4-chlorophenol removal from aqueous solutions: Use of free and immobilized soybean peroxidase and KrCl excilamp. *J Hazard Mater.* 169, 46-51.
- Han, DH; Cha, SY; Yang, HY (2004). Improvement of oxidative decomposition of aqueous phenol by microwave irradiation in UV/H₂O₂ process and kinetic study. *Water Res.*, 38, pp. 2782-2790.
- Krýsa, J; Waldner, G; Měšt'ánková, H; Jirkovský, J; Grabner, G (2006). Photocatalytic degradation of model organic pollutants on an immobilized particulate TiO₂ layer: Roles of adsorption processes and mechanistic complexity. *Appl Catal Environ.* 64, 290-301.
- Kuo, WS; Lin, IT (2009). Biodegradability of chlorophenol wastewater enhanced by solar Photo-Fenton process. *Water Sci Technol*, 59 (5): 973-978
- Lai, TL; Liu, JY; Yong, KF; Shu, YY; Wang, CB (2008). Microwave-enhanced catalytic degradation of 4-chlorophenol over nickel oxides under low temperature. *J Hazard Mater.* 157, 496-502.
- Lai, T-L; Wang, W-F; Shu, Y-Y; Liu, Y-T; Wang, C-B (2007). Evaluation of microwave-enhanced catalytic degradation of 4-chlorophenol over nickel oxides. *J. Mol Catal A Chem.*, 273, 303-309.
- Li, J M; Meng, XG; Hu, CW; Du, J; Zeng, XC (2008). Oxidation of 4-chlorophenol catalyzed by Cu (II) complexes under mild conditions: Kinetics and mechanism. *J. Mol Catal A Chem.*, 299: 102-107.
- Lin, C-F; Wu, C-H; Onn, Z-N (2008). Degradation of 4-chlorophenol in TiO₂, WO₃, SnO₂, TiO₂/WO₃ and TiO₂/SnO₂ systems. *J Hazard Mater.* 154, 1033-1039.
- Lo, SC; Lin, CF; Wu, CH; Hsieh, PH (2004). Capability of coupled CdSe/TiO₂ for photocatalytic degradation of 4-chlorophenol. *J Hazard Mater.* 114, 183-190.
- Marianna, C (2005). Photo-degradation of chlorophenols in the aqueous solution. *J Hazard Mater.* 134, 45-59.
- Movahedyan, H; Assadi, A; Amin, MM (2008). Effects of 4-chlorophenol loadings on acclimation of biomass with optimized fixed time sequencing batch reactor. *Iran J Environ Health Sci Eng.*, 5, 225-234.
- Movahedyan, HS; Mohammadi, AM; Assadi, A (2009). Comparison of Different Advanced Oxidation Processes Degrading P-Chlorophenol in Aqueous Solution. *Iran J Environ Health Sci Eng.*, 6, 153-160.
- Olaniran, AO; Igbinsola, EO (2011). Chlorophenols and other related derivatives of environmental concern: Properties, distribution and microbial degradation processes. *Chemosphere.* 83, 1297-1306.
- Pera-Titus, M; García-Molina, V; Baños, MA; Giménez, J; Esplugas, S (2003). Degradation of chlorophenols by means of advanced oxidation processes: a general review. *Appl Catal Environ*, 47, 219-256.
- Pi, Y; Zhang, L; Wang, J; (2007). The formation and influence of hydrogen peroxide during ozonation of para-chlorophenol. *J Hazard Mater.* 141, 707-712.
- Seo, JK; Ki-Joon, J; Young-Kwon, P; Sangmin, J; Heon, L; Sang-Chul, J; (2017). Improving removal of 4-chlorophenol using a TiO₂ photocatalytic system with microwave and ultraviolet tradition. *Catalysis Today.* 293-294. 15-22.
- Stoyanova, M; Christoskova, S (2011). Catalytic degradation of methylene blue in aqueous solutions over Ni- and Co- oxide systems. *Cent Eur J Chem.*, 9, 1000-1007.
- Stoyanova, M; Christoskova, S; Georgieva, M (2003). Mixed Ni-Mn-oxide systems as catalysts for complete oxidation: Part I. Preparation and characterization. *Appl Catal A Gen.*, 249, 285-294.
- Tabatabaei, SM; Dastmalchi, S; Mehrizad, A; Gharbani, P (2011). Enhancement of 4-nitrophenol ozonation in water by nano ZnO catalyst. *Iran J Environ Health Sci Eng.*, 8, 363-372.
- Westmeier, F; Rehm, HJ (1987). Degradation of 4-chlorophenol in municipal wastewater by adsorptive immobilized *Alcaligenes* sp. A 7-2. *Applied Microbiology and Biotechnology.* 26, (1). 78-83.