



## Corn Stover as Substrate for Biogas Generation and Precursor for Biosilica Production via Anaerobic Digestion

Akinola D Olugbemide<sup>1\*</sup>, Lajide Labunmi<sup>2</sup>, Ikhazuagbe H Ifijen<sup>3</sup> and Damilare I Ogungbemide<sup>4</sup>

<sup>1</sup>Department of Basic Sciences, Auchi Polytechnic, Auchi, Edo State Nigeria

<sup>2</sup>Department of Chemistry, Federal University of Technology Akure, Ondo State, Nigeria

<sup>3</sup>Department of Research Operations, Rubber Research Institute of Nigeria, Benin City, Nigeria

<sup>4</sup>5657 Spring Garden Road, Suite 705, Halifax, Nova Scotia B3J 3R4

Corresponding author, e-mail: [akinoladave@gmail.com](mailto:akinoladave@gmail.com); [akinolaore@auchi.edu.ng](mailto:akinolaore@auchi.edu.ng)

Co-authors e-mail addresses: [bmlajide@gmail.com](mailto:bmlajide@gmail.com); [larylans4u@yahoo.com](mailto:larylans4u@yahoo.com); [bennyidlife@yahoo.com](mailto:bennyidlife@yahoo.com)

Received 6 August 2020, Revised 9 Oct 2020, Accepted 13 Oct 2020, Published Oct 2020

### Abstract

Production of fuels and chemicals from renewable biomass is crucial to sustainability of bio-based economy. In this study, anaerobic digestion of corn stover (CS) was carried out to produce biogas under mesophilic conditions. The study also investigated the potential of corn stover digestate ash as a potential source for biosilica production. A cumulative volume of 930 mL of biogas was produced with methane content of 85.87%. Higher and lower calorific values of biogas were calculated to be 36.30 MJ/m<sup>3</sup> and 32.70 MJ/m<sup>3</sup>, respectively. Calcination of raw CS (RCS) and the digestate (CSD) was carried out at 600 °C for 3 hours. The samples generated, raw corn stover ash (RCSA) and corn stover digestate ash (CSDA) were characterized using X-ray fluorescence (XRF), Fourier transform infrared (FTIR) spectroscopy, scanning electron microscope (SEM), and X-ray diffractometer (XRD). The XRF results revealed that CSDA biosilica content was 60.49%, which was 34.84% higher than RCSA. There was reduction in most of the metallic impurities in CSDA compared to RCSA. Potassium oxide was drastically reduced from 12.34% to 1.60%, while Al<sub>2</sub>O<sub>3</sub> was reduced from 7.17% to 6.95%. SEM images showed the changes in the surface morphology of RCSA and CSDA, while FTIR spectra identified the changes in the key functional groups present in the samples. The study showed that CS and its digestate could serve as profitable renewable feedstocks for bioenergy production and bio-based chemicals like silica.

**Keywords:** Anaerobic Digestion; Biogas; Biosilica; Corn Stover; Digestate; Calorific Value

### Introduction

Global transition to clean energy and production of value-added chemicals and materials from renewable sources based on the concept of biorefinery comes with its challenges and opportunities (Philp 2018). One of such challenges is in the area of anaerobic digestion (AD) where enormous quantities of digestates are generated. AD is

an environmentally benign technology that converts organic biomass to biogas (methane and carbon dioxide) with the aid of microorganisms in the absence of oxygen (González et al. 2018). The digestates which are the by-products of AD are made up of liquid and solid fractions that are mostly used as biofertilizers (Koszel and Lorencowicz 2015). However, with AD technology gaining

prominence and acceptance in many quarters as alternative source of energy, large quantities of digestates are equally produced that need to be managed appropriately. Although some research efforts aimed at increasing and providing alternative use for digestates have been carried out (Achinah et al. 2017, Czekala 2017, Kaur et al. 2020) yet a lot still has to be done as a forward-thinking approach to mitigate the problems from unused digestates. For instance, biofuels like briquettes and pellets have been produced from solid fractions of digestates (Czekala 2017, Czekala et al. 2018). There is need for sustainable techniques to produce more valued-added products from these digestates in order to increase their usefulness, prevent their being sources of environmental concern and invariably enhance competitiveness of bio-based industries. Otherwise, in a bid to solve one problem we may be unwittingly creating another with far reaching effects on humans and the environment.

Mirmohamadsadeghi and Karimi (2018) produced amorphous silica from the ash of digestate from rice straw in a more environmentally friendly manner than the capital intensive conventional method of producing silica. Numerous temperature regimes have been used to prepare biosilica with the conclusion that combustion temperature and time played crucial roles in producing biosilica of high quality (Terzioğlu et al. 2019). Silica finds applications in various industries such as food, paint, and cosmetics industries (Permatasari et al. 2016).

Corn stover (CS) is an agricultural waste remaining in the field after harvesting corn (Paul et al. 2019). Corn is a major staple crop in Nigeria that enjoys two planting seasons in a year, thus huge amounts of it are produced annually. Nigeria is the tenth largest producer of corn in the world and the highest in Africa (IITA 2020). Therefore, corn stover is one of the major agricultural wastes produced in Nigeria and it is highly underutilized for any profitable uses. Production of second generation biofuels like biogas and other

value added products like silica from CS would help convert a liability to valuable asset. However, it is worth mentioning that corn stover can be used for erosion control and it is also a source of soil nutrients like phosphorus and potassium (Bashagaluke et al. 2018, Wang et al. 2007). The objectives of the study therefore were to produce biogas from CS under mesophilic conditions, calculate its calorific value, and evaluate the biosilica potential of the ash of the digestate using XRF, FTIR, SEM, XRD in comparison with the ash of raw CS.

### **Materials and Methods**

Corn stover was collected in June 2018 from a local farm in Irrua in Esan Central Local Government Area, Edo State, Nigeria. The corn stover was sun-dried for three weeks and pulverized to reduce the particle size. Afterwards, the sample was passed through a 600 microns mesh sieve. The sample was stored in an air-tight container prior to analysis and anaerobic digestion.

### **Anaerobic digestion**

Batch laboratory AD of raw corn stover (RCS) was carried out at particle size of 600 microns. A sample of 100 grams was mixed with 400 mL of water (solid-to-liquid ratio of 1:4) and charged into a 1-L glass bioreactor for a retention time of twenty-one days at an ambient temperature of  $26 \pm 1$  °C. Cumulative biogas produced was measured by downward displacement method with saturated salt solution every 24 hours (Adamu 2014). Initial and final pH values were measured using a digital pH meter by HANNA Instruments. Methane content was determined using chemical absorption method as described by Lasocki et al. (2015). Volatile solid reduction (VSR) was calculated by the method described by Puyuelo et al. (2011). Higher calorific value (HCV) and lower calorific value (LCV) of biogas from the digester were determined according to the following formula:

$$HCV_{\text{biogas}} = 0.3989 \times MC + 0.0213 \quad (1)$$

$$LCV_{\text{biogas}} = 0.3593 \times MC + 0.0192 \quad (2)$$

### Characterization of raw corn stover and digestate corn stover

Moisture content, total solid, ash content, carbon, nitrogen, lignin, cellulose and hemicellulose of raw CS and the solid fraction of its digestate were determined using standard methods (ASTM 1972, Horwitz 2000).

### Preparation of ashes of raw corn stover and digestate

The solid fraction of corn stover digestate was separated from the liquor and sun-dried for three days. The dried digested CS was calcined at 600 °C for 3 hours along with the raw CS. The resulting raw corn stover ash (RCSA) and corn stover digestate ash (CSDA) were kept in air-tight containers for analyses.

### Characterization of raw corn stover ash and corn stover digestate ash

The chemical compositions of raw corn stover ash (RCSA) and corn stover digestate ash (CSDA) were determined using an energy dispersive X-ray fluorescence (XRF; Xsupreme 8000 Model, Oxford Instrument). The X-ray diffraction (XRD) patterns of RCSA and DCSA samples were recorded using XPert PRO model, Netherlands. The samples were scanned in the  $2\theta$  range of 5° to 90°. The functional groups were determined using FTIR spectroscopy, while surface morphology was carried out using SEM.

## Results and Discussion

### Anaerobic digestion of corn stover

Table 1 shows physicochemical properties of raw CS and its digestate. There was increase in ash content after anaerobic digestion which is an indication of increased mineral content in the digestate. This shows that the digestate could be used as a biofertilizer (Dahunsi et al. 2019). A high VS/TS ratio of 0.84 was a confirmation that

the substrate had appreciable quantity of digestible organic materials. The VS/TS was similar to 0.87 reported for banana peel waste by Achinas et al. (2019). There was increase in lignin and hemicellulose contents after anaerobic digestion; this observation has been reported in literature (Waliszewska et al. 2019). The cellulose content in the raw sample was relatively high, which is beneficial for anaerobic digestion. The reduction in the cellulose content after digestion revealed that the microorganisms were capable of degrading the cellulose for bioenergy generation. Initial pH value was 6.50, while the final pH was 3.10; this obvious reduction in pH has been attributed to the increase in volatile fatty acid production during AD process (Xu et al. 2013).

**Table 1:** Physicochemical properties of raw corn stover and corn stover digestate


Parameters (%)	Raw corn stover	Corn stover digestate
Moisture content	3.00	7.00
Ash content	15.27	24.45
Total solids	97.00	93.00
Volatile solids	81.73	68.55
*VS/TS	0.84	0.74
Lignin	12.30	15.50
Cellulose	53.30	48.74
Hemicellulose	34.40	35.76

\*VS/TS has no unit.


Daily biogas production from raw CS is shown in Figure 1. Biogas production commenced on day 1 which revealed that the initial lag phase was short, which is an indication of rapid acclimatization of the microorganisms to the substrates. However, there was a decline in production after some days followed by days of little (represented by short peaks) or no production till the end of the experiment. Kafle and Kim (2013) have suggested that the diauxic phase experienced in the biogas production could be attributed in part to the presence of easily digestible and non-easily digestible

components in the substrate. Figure 2 shows cumulative biogas production of the sample which was 930 mL at the expiration of the digestion process. Volatile solid reduction (VSR) was calculated to be 50.97%, which was similar to 50.49% reported for anaerobically digested cow manure in a hydraulic mixed Chinese dome digester by Jegede et al. (2019). Cumulative methane content from RCS was calculated to be 85.87% using chemical absorption method. This value was higher than 72.30% reported by Pertiwinigrum et al. (2018). Equations 1 and 2 were used to calculate the  $HCV_{biogas}$

and  $LCV_{biogas}$  for methane in this study, which were  $34.28 MJ/m^3$  and  $30.87 MJ/m^3$ . The values for  $HCV_{biogas}$  and  $LCV_{biogas}$  were comparable to  $36.30 MJ/m^3$  and  $32.70 MJ/m^3$  reported for anaerobic codigestion of buffalo grass and dung by Chuanchai and Ramaraj(2018). On the other hand, the values were higher than  $23.8 MJ/m^3$  and  $21.50 MJ/m^3$  reported for municipal solid wastes by Triana-Jiménez et al. (2019). The  $HCV_{biogas}$  and  $LCV_{biogas}$  for CS seem satisfactory when compared to that of pure methane which is  $39.82 MJ/m^3$  and  $35.87 MJ/m^3$ , respectively (Li et al. 2017).

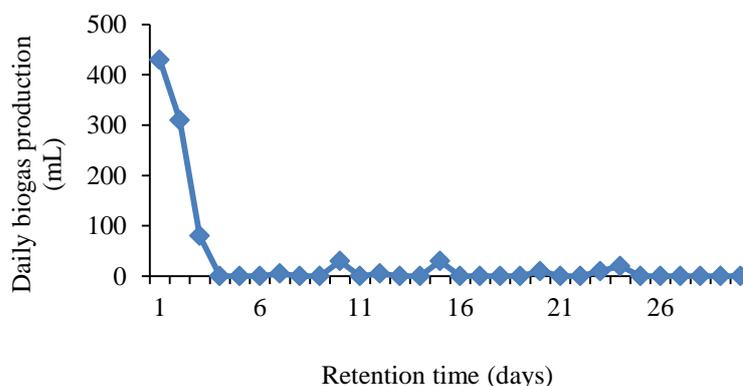

**Figure 1:** Daily biogas production of corn stover.

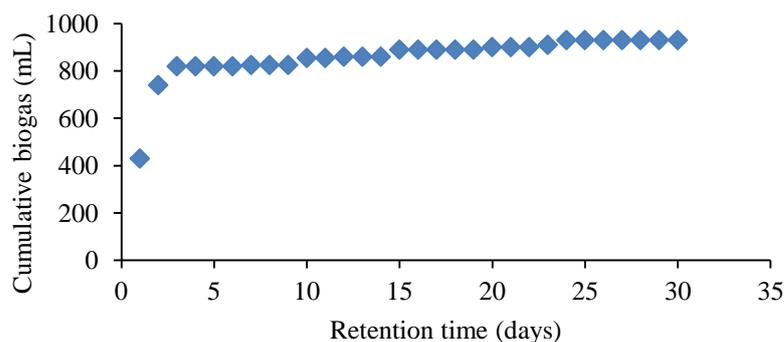

**Figure 2:** cumulative biogas production from corn stover.

**Chemical analysis of RCSA and CSDA**

Chemical composition results for RCSA and CSDA are shown in Table 2. The  $SiO_2$  content of CSDA was 60.49% which was 34.84% higher than that of RCSA. The value

obtained for  $SiO_2$  in CSDA was higher than the 39.95% and 43.22% reported for maize stalk and wheat hull by Terzioğlu et al. (2013),but lower than the 71.50% recorded for raw bagasse ash by Tadesse et al. (2019).

There was a significant reduction in  $K_2O$  impurity after anaerobic digestion from 12.34% to 1.60% but not  $Na_2O$  which increased significantly after AD. The decrease in  $K_2O$  after AD is in agreement with the findings of Mirmohamadsadeghi and Karimi (2018) on the production of amorphous nanosilica from rice stalk digestate. A decrease in the contents of  $Al_2O_3$  and  $SO_3$  was also observed. This is

advantageous as their presence in high amount has been implicated for reduced usefulness of biosilica (Adebisi et al. 2017). The observed reduction in metallic oxides as a result of AD is indicative of higher purity and a welcome development from economic standpoint since removal of impurities in biosilica is normally carried out by a relatively expensive acid leaching method (Khalifa et al. 2012, Suryanto et al. 2018).

**Table 2:** Chemical analysis of RCSA and CSDA by X-ray fluorescence

Sample	SiO <sub>2</sub>	K <sub>2</sub> O	CaO	MgO	Na <sub>2</sub> O	Al <sub>2</sub> O <sub>3</sub>	P <sub>2</sub> O <sub>5</sub>	Fe <sub>2</sub> O <sub>3</sub>	Mn <sub>2</sub> O <sub>3</sub>	Cl	SO <sub>3</sub>	TiO <sub>2</sub>
RCSA	44.86	12.34	6.20	5.81	0.95	7.17	8.44	8.65	0.17	0.97	3.55	0.73
CSDA	60.49	1.60	4.18	2.24	4.34	6.95	2.98	10.02	0.13	2.80	3.08	1.03

Physical appearances of RCSA and CSDA are shown in Figure 3. The ash of RCSA was greyish in colour, while that of CSDA was brownish. The variation in colour could be as a result of the transition metal oxides present in the samples (Terzioğlu et al. 2019)



**Figure 3:** Physical appearances of a) raw corn stover ash (RCSA) b) corn stover digestate ash (CSDA).

#### Functional groups analysis of the studied corn stover samples


Figure 4 shows the infrared spectra of the corn stover digestate (CSD), corn stover digestate ash (CSDA), raw corn stover (RCS) and raw corn stover ash (RCSA) with different levels of intensity. The Si-OH (silanol) peak at about  $3130-3712\text{ cm}^{-1}$  (Mirmohamadsadeghi and Karimi 2018) is evident in all the samples. The appearance of the band at  $2844-2988\text{ cm}^{-1}$  in the spectrum

of the CSD and RCS is attributed to the stretching of  $CH_2$  bonds of polysaccharides (Mirmohamadsadeghi and Karimi 2018). The observed band was absent in the CSDA and RCSA samples after subjecting them to calcination. This could be due to the degradation of the polysaccharides molecules brought about by calcination at  $600\text{ }^\circ\text{C}$  for 3 hours. This is a clear indication that calcination carried out on the samples at this temperature had brought about some significant changes in the samples. The calcination temperature of  $600\text{ }^\circ\text{C}$  used in this study falls within the range reported in literature as appropriate for the production of biosilica (Memon et al. 2020, Wang et al. 2019).

Sharp bands were visible in the spectra at  $1628\text{ cm}^{-1}$  for lignin moieties (Chen et al. 2012, Pandey 1999) in all the samples (CSD, CSDA, RCS and RCSA). The peak at  $1386\text{ cm}^{-1}$  in the spectrum of the CSD, CSDA and RCS samples are suggestive of the presence of weak C-O stretching in cellulose (Wetzel et al. 1998, Xu et al. 2013, Yu et al. 2007). However, this peak was not observed in the spectrum of RCSA, instead, there was an appearance of a broad peak at  $1368-1530\text{ cm}^{-1}$ . The peak at  $796\text{ cm}^{-1}$  can be ascribed to the symmetric vibration of Si-O (Mirmohamadsadeghi and Karimi 2018) in CSD and CSDA. The absence of this peak in

the RCS and RCSA samples maybe because they were not subjected to anaerobic digestion. The peak of aliphatic C-O-C groups at 1028–1092  $\text{cm}^{-1}$  can be attributed to the presence of hemicellulose and cellulose (Rafiq et al. 2016) in all the samples. This is indicative of incomplete charring of the

RCSA and CSDA, at this temperature (Chen et al. 2008, Rafiq et al. 2016). The peak at 466  $\text{cm}^{-1}$  observed in all the studied samples has been attributed to the presence of silica (O-Si-O) ( Ifijen et al. 2020, Mirmohamadsadeghi and Karimi 2018).

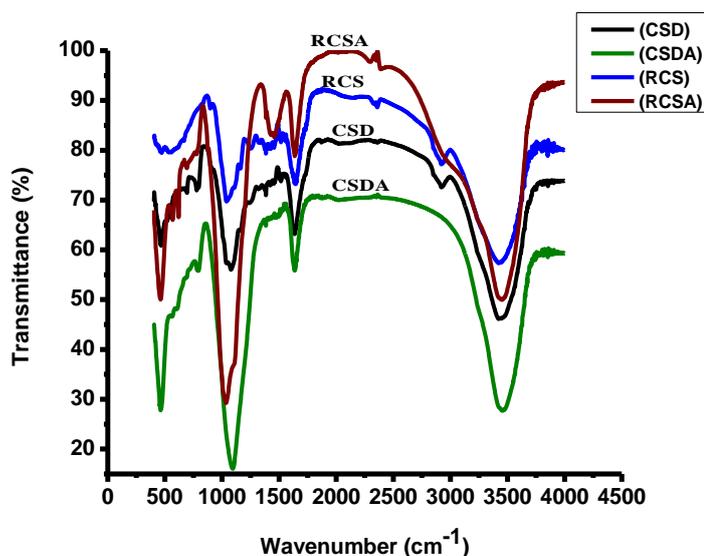

**Figure 4:** FTIR spectra of raw corn stover (RCS), raw corn stover ash (RCSA), corn stover digestate (CSD) and corn stover digestate ash (CSDA).

#### **Analysis of the crystalline and amorphous nature of CSDA and RCSA samples**


Figure 5 shows the XRD pattern of the samples of raw corn stover ash (RCSA) and corn stover digestate ash (CSDA). XRD results revealed the emergence of multiple peaks at several regions of the raw corn stover ash. Narrow peaks were located at  $2\theta$  values of 7.9°, 9.5°, 11.3°, 12.5°, 17.1°, 21°, 23.0°, 26.5° and 30.1°. Broad peaks which were not intense were also observed in other regions of the RCSA. The observed results are indications that the analyzed RCSA had more crystalline regions than amorphous regions. The observed peaks may also be due to the presence of the elemental oxides impurities detected by the XRF (Table 2) and cellulose lattice. On digestion of the studied

material, most of the aforementioned peaks that appeared before anaerobic digestion disappeared completely leaving behind two narrow intense peaks at  $2\theta$  values 21.0° and 23.5° for the corn stover digestate ash (CSDA). The observed two narrow, sharp peaks at  $2\theta$  values around 21.5° and 23.8° could be attributed to the partial crystalline regions of the cellulose content and silica regions, respectively (Fernandes et al. 2017, Singh et al. 2015).

The peaks have been attributed to the presence of cristobalite, a crystalline form of silica (Fernandes et al. 2017). The disappearance of the numerous peaks in CSDA could be indicative of reduction in its crystalline nature. The peak that appeared at the angle of 23.5° can be attributed to the presence of partial crystalline silica.

However, the silica synthesized via other sources at  $2\theta = 23.5$  have been shown by several studies to be completely amorphous

in nature (Fernandes et al. 2017, Kalapathy et al. 2000, Kamath and Proctor 1998).

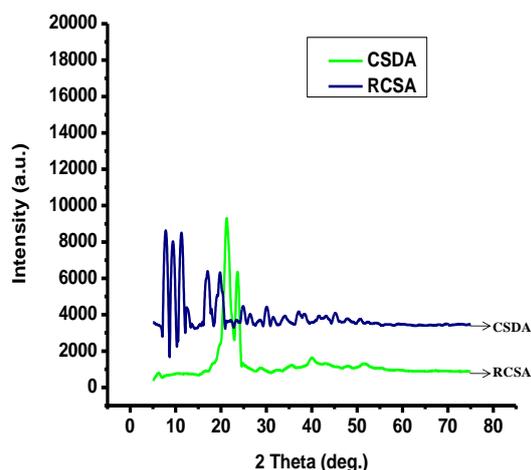


**Figure 5:** X-ray powder diffraction (XRD) spectra of ashes of raw and digested corn stover

**Morphology of the RCSA and CSDA samples**

Figure 6 shows the SEM mages of samples RCSA and CSDA. Sample RCSA had a coarse, clustered surface, while sample

CSDA had lesser clustered surface (loosened) and more porous than RCSA. Activities of the anaerobic microorganisms could have been responsible for the observed changes.

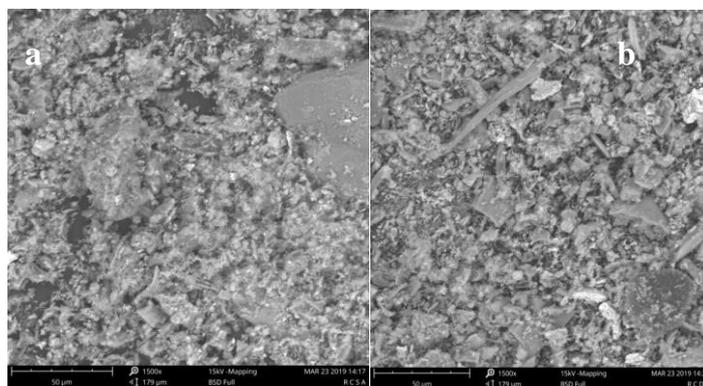

**Figure 6:** The SEM images of a) raw corn stover ash and b) corn stover digestate ash.

**Conclusion**

This study revealed that CS is a valuable substrate for biogas production with high methane content of 85.87%. The high calorific value of 36.30 MJ/m<sup>3</sup> obtained in this work further proved the quality of biogas from CS. The SEM images revealed that

CSDA was more porous and less coarse than RCSA, while the XRD results showed that CSDA had less crystalline regions. CSDA showed a remarkable improvement in biosilica content in comparison to RCSA as revealed by the XRF. The results further demonstrated that CSDA had higher

purity than RCSA based on reduction in metallic oxides impurities which was an indication that AD was effective in reducing some of the metallic impurities. Therefore, AD could serve as an alternative to relatively expensive chemical treatment usually employed to improve the quality of biosilica, while at the same time increasing product yields.

**Conflicts of interest/Competing interests:**

The authors declare no conflict of interest.

**References**

- Achinas S, Achinas V and Euverink GJW 2017 A technological overview of biogas production from biowaste. *Engineering* 3(3): 299-307.
- Achinas S, Krooneman, J and Euverink GJW 2019 Enhanced biogas production from the anaerobic batch treatment of banana peels. *Engineering* 5(5): 970-978.
- Adamu AA 2014 Effect of substrate on biogas yield. *Global J. Engineering Res.* 13(1): 35-39.
- Adebisi JA, Agunsoye JO, Bello SA, Ahmed II, Ojo OA and Hassan SB 2017 Potential of producing solar grade silicon nanoparticles from selected agro-wastes: are view. *Solar Energy* 142 (68): 68-86.
- ASTM (American Society for Testing and Materials) 1972 Standard methods of test for alcohol-benzene solubility of wood. ASTM D1 107-56.
- Bashagaluke JB, Logah V, Opoku A, Sarkodie-Addo J and Quansah C 2018 Soil nutrient loss through erosion: impact of different cropping systems and soil amendments in Ghana. *PloS one* 13(12): e0208250.
- Chen B, Zhou D and Zhu L 2008 Transitional adsorption and partition of nonpolar and polar aromatic contaminants by biochars of pine needles with different pyrolytic temperatures. *Environ. Sci. Technol.* 42 (14): 5137-5143.
- Chen WH, Ye SC and HK S 2012 Hydrolysis characteristics of sugarcane bagasse pretreated by dilute acid solution in a microwave irradiation environment. *Appl. Energy* 93: 237-244.
- Chuanchai A and Ramaraj R 2018 Sustainability assessment of biogas production from buffalo grass and dung: biogas purification and bio-fertilizer. *Biotech* 8(3): 151.
- Czekala W 2017 Processing digestate from agricultural biogas plant to obtain financial and environmental benefits. *In HAICTA* 188-195.
- Czekala W, Bartnikowska S, Dach J, Janczak D, Smurzyńska A, Kozłowski K, Bugała A, Lewicki A, Cieślak M, Typańska D and Mazurkiewicz J 2018 The energy value and economic efficiency of solid biofuels produced from digestate and sawdust. *Energy* 159: 1118-1122.
- Dahunsi SO, Adesulu-Dahunsi AT, Osueke CO, Lawal AI, Olayanju TMA, Ojedoran JO and Izebere JO 2019 Biogas generation from *Sorghum bicolor* stalk: effect of pretreatment methods and economic feasibility. *Energy Rep.* 5: 584-593.
- Fernandes IJ, Calheiro D, Sánchez FAL, Camacho ALD, Rocha TLADC, Moraes CAM and Sousa VCD 2017 Characterization of silica produced from rice husk ash: comparison of purification and processing methods. *Materials Res.* 20: 512-518.
- González J, Sánchez ME and Gómez X 2018 Enhancing anaerobic digestion: the effect of carbon conductive materials. *J. Carbon Res.* 4(4): 59.
- Horwitz W 2000 Official methods of analysis of AOAC International AOAC International, Gaithersburg, Md.
- IITA (International Institute for Tropical Agriculture. Growing in Nigeria) 2020 Commercial crop production guide series. information and communication support for agricultural growth in Nigeria. USAID 1-8.
- Ifijen IH, Itua AB, Maliki M, Ize-Iyamu CO, Omorogbe SO, Aigbodion AI, Ikhuoria

- EU 2020 The removal of nickel and lead ions from aqueous solutions using green synthesized silica microparticles, *Heliyon* 6: e04907.
- Jegede AO, Zeeman G and Bruning H 2019 Effect of mixing regimes on cow manure digestion in impeller mixed, unmixed and Chinese dome digesters. *Energies* 12(13), 2540.
- Kafle GK and Kim SH 2013 Anaerobic treatment of apple waste with swine manure for biogas production: batch and continuous operation. *Appl. Energy* 103: 61-72.
- Kalapathy U Proctor A and Shultz J 2000 A simple method for production of pure silica from rice hull ash. *Bioresour. Technol.* 73(3): 257-262.
- Kamath SR and Proctor A 1998 Silica gel from rice hull ash: preparation and characterization. *Cereal Chem.* 75(4): 484-487.
- Kaur G, Wong JWC, Kumar R, Patria RD, Bhardwaj A, Uisan K and Johnravindar D 2020 Value addition of anaerobic digestate from biowaste: thinking beyond agriculture. *Curr. Sustain. Renew. Energy Rep.* 7(2): 48-55.
- Khalifa M, Hajji M and Ezzaouia H 2012 Impurity removal process for high-purity silica production by acid leaching. In "European Physical Journal Web of Conferences", Vol. 29, pp. 00014, EDP Sciences.
- Koszel M and Lorencowicz E 2015 Agricultural use of biogas digestate as a replacement fertilizers. *Agric. Agric. Sci. Proc.* 7: 119-124.
- Lasocki J, Kołodziejczyk K and Matuszewska A 2015 Laboratory-scale investigation of biogas treatment by removal of hydrogen sulfide and carbon dioxide. *Polish J. Environ. Studies* 24: 1427-1434.
- Li Y, Liu H, Yan F, Su D, Wang Y and Zhou H 2017 High-calorific biogas production from anaerobic digestion of food waste using a two-phase pressurized biofilm (TPPB) system. *Bioresour. Technol.* 224: 56-62.
- Memon SA, Khan S, Wahid I, Shestakova Y and Ashraf M 2020 Evaluating the effect of calcination and grinding of corn stalk ash on pozzolanic potential for sustainable cement-based materials. *Advanc. Mater. Sci. Engin.* 2020: 1619480.
- Mirmohamadsadeghi S and Karimi K 2018 Energy recovery together with amorphous nanosilica production from rice straw via dry anaerobic digestion. *Bioresources* 13(1): 1872-1884.
- Pandey KK 1999 A study of chemical structure of soft and hardwood and wood polymers by FTIR spectroscopy. *J. Appl. Polymer Sci.* 71(12): 1969-1975.
- Paul S, Dutta A, Thimmanagari M and Defersha F 2019 Techno-economic assessment of corn stover for hybrid bioenergy production: a sustainable approach. *Case Studies in Thermal Engineering* 13: 100408.
- Permatasari N, Sucharya TN and Nandiyanto ABD 2016 Review: agricultural wastes as a source of silica material. *Indones. J. Sci. Technol.* 11(1): 82-106.
- Pertiwinigrum A, Harto AW, Wuri MA and Budiarto R 2018 Assessment of calorific value of biogas after carbon dioxide adsorption process using natural zeolite and Biochar. *Int. J. Environ. Sci. Develop.* 9(11): 327-330.
- Philp J 2018 The bioeconomy, the challenge of the century for policy makers. *New Biotechnol.* 40 (Pt A): 11-19.
- Puyuelo B, Ponsá S, Gea T and Sánchez A 2011 Determining C/N ratios for typical organic wastes using biodegradable fractions. *Chemosphere* 85 (4): 653-659.
- Rafiq MK, Bachmann RT, Rafiq MT, Shang Z, Joseph S and Long R 2016 Influence of pyrolysis temperature on physico-chemical properties of corn stover (*Zea mays* L.) biochar and feasibility for carbon capture and energy balance. *PLoS One* 11(6): e0156894.

- Singh S, Cheng G, Sathitsuksanoh N, Wu D, Varanasi P, George A, Balan V, Gao X, Kumar R, Dale BE, Wyman CE and Simmons BA 2015 Comparison of different biomass pretreatment techniques and their impact on chemistry and structure. *Front. Energy Res.* 2: 62.
- Suryanto BHR, Fang T, Cheong S, Tilley RD and Zhao C 2018 From the inside-out: leached metal impurities in multiwall carbon nanotubes for purification or electrocatalysis. *J. Mater. Chem. A* 6 (11): 4686-4694.
- Tadesse M, Amare E, Murthy HCA and EB 2019 Extraction and characterization of biosilica from sugarcane bagasse ash of Wonji sugar industry Ethiopia. *Int. J. Res. Anal. Rev. (IJRAR)* 6 (3): 609-618.
- Terzioğlu P, Yücel S and Kuş Ç 2019 Review on a novel biosilica source for production of advanced silica-based materials: wheat husk. *Asia-Pacific J. Chem. Engin.* 14(1): e2262.
- Terzioğlu P, Yucel S, Rabagah TM and Özçimen D 2013 Characterization of wheat hull and wheat hull ash as a potential source of SiO<sub>2</sub>. *BioResource* 8 (3): 4406-4420.
- Triana-Jiménez KM and Velásquez Lozano ME 2019 Comparison of biogas production obtained from samples of Mitú and Sibundoy municipal solid waste. *Ingen. Investig.* 39(2): 31-36.
- Waliszewska H, Zborowska M, Stachowiak-Wencek A, Waliszewska B and Czekala W 2019 Lignin transformation of one-year-old plants during anaerobic digestion (AD). *Polymers* 11(5): 835.
- Wang F, Zhang D, Chen M, Yi W and Wang L 2019 Characteristics of corn stover components pyrolysis at low temperature based on detergent fibers. *Frontiers in Bioengineering and Biotechnol.* 7: 188-188.
- Wang X, Cai D, Hoogmoed WB, Perdok UD and Oenema O 2007 Crop residue, manure and fertilizer in dryland maize under reduced tillage in northern China: I grain yields and nutrient use efficiencies. *Nutr. Cycl. Agroecosyst.* 79(1): 1-16.
- Wetzel DL, Eilert AJ, Pietrzak LN, Miller SS and Sweat JA 1998 Ultraspatially-resolved synchrotron infrared microspectroscopy of plant tissue in situ. *Cell. Mol. Biol. (Noisy-le-Grand, France)* 44(1): 145-168.
- Xu F, Yu J, Tesso T, Dowell F and Wang D 2013 Qualitative and quantitative analysis of lignocellulosic biomass using infrared techniques: A mini-review. *Appl. Energy* 104: 801-809.
- Yu P, Block H, Niu Z and Doiron K 2007 Rapid characterization of molecular chemistry, nutrient make-up and microlocation of internal seed tissue. *J. Synchronr. Radiat.* 14(4): 382-390.